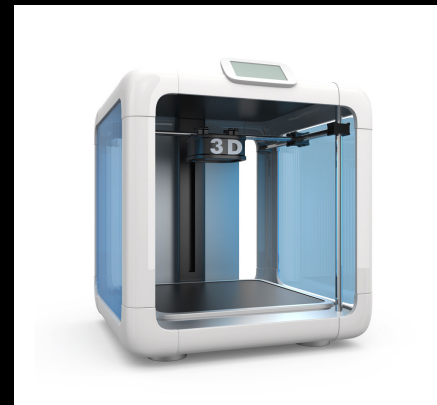

Chroma Color's Processing Conditions Polycarbonate

Guidelines for Polycarbonate Processing

This information is intended only as a guideline for designers and processors of modified thermoplastics for injection molding. Because injection mold design and processing is complex, a set solution will not solve all problems. Observation on a "trial and error" basis may be required to achieve desired results.



For more information on **Polycarbonate Processing**

815-385-8100

<https://chromacolors.com>



Chroma Color's Processing Conditions Polycarbonate Information

Processing Conditions Polycarbonate

Typical Injection Molding Conditions	English	SI Metric
Rear zone	520 - 550 °F	271 - 288 °C
Center zone	540 - 570 °F	282 - 299 °C
Front zone	560 - 590 °F	293 - 310 °C
Melt	550 - 600 °F	288 - 316 °C
Mold	180 - 250 °F	82 - 121 °C
Injection	10000 - 15000 psi	69 - 103 MPa
Hold	5000 - 12000 psi	34 - 83 MPa
Back	50 - 100 psi	0.34 - 0.69 MPa
Fill	1 - 2 in/sec	25 - 51 mm/sec
Screw	60 - 90 rpm	60 - 90 rpm
Time & Temperature	4 Hrs @ 250 °F	4 Hrs @ 121 °C
Dew Point	-20 °F	-29 °C
Moisture Content	0.02 %	0.02 %

No information supplied by Chroma Color Corporation constitutes a warranty regarding product performance or use. Any information regarding performance or use is only offered as a suggestion for investigation for use, based upon Chroma Color Corporation or other customer experience. Chroma Color Corporation makes no warranties, expressed or implied, concerning the suitability or fitness of any of its products for any particular purpose. It is the responsibility of the customer to determine that the product is safe, lawful and technically suitable for the intended use. The disclosure of information herein is not a license to operate under, or recommendation to infringe any patents.

For more information on Polycarbonate Processing
815-385-8100
<https://chromacolors.com>